

IOG-2 Phosphate Laser Glass

For High Gain Applications

IOG-2 is a potassium-barium-alumino phosphate glass with high erbium and ytterbium cross sections for stimulated emission. Although not as chemically durable as IOG-1, IOG-2 is an excellent candidate for active photonic devices that require high gain.

Optical Properties

n_d	1.518
V_d	66.8
$n_{1000\text{ nm}}$ (calculated)	1.510
$n_{1540\text{ nm}}$ (calculated)	1.508

Erbium Laser Properties

Emission Maxima, λ (nm)	1533
Emission Cross Section at 1533 nm (10^{-21} cm ²)	8.0
Excited State Lifetime for the 1533 nm Band (ms)	9.0
Max Absorption Cross Section for 980 nm Pump Band (10^{-21} cm ²)	2.4

Ytterbium Laser Properties

Emission Maxima, λ (nm)	1000
Emission Cross Section at 1000 nm (10^{-21} cm ²)	5.4
Excited State Lifetime for the 1000 nm Band (ms)	1.5
Max Absorption Cross Section for 980 nm Pump Band (10^{-21} cm ²)	14.1

• Properties will vary slightly with doping content

Chemical Properties

Weight Loss in 50 °C Water [mg/(cm ² x day)]	0.028
Acid Resistance SR pH = 0.3 at 25 °C	4.0
Alkali Resistance AR pH = 12 at 50 °C	4.0
Staining Resistance FR pH = 4.6 100 h at 25 °C	1
Climatic Resistance CR Water Vapor at 40–50 °C for 30 h	2


Physical Properties

Density, ρ [g/cm ³]	2.72
Thermal Conductivity (25 °C), κ [W/m x K]	0.57
Young's Modulus, E [GPa]	54
Poisson's Ratio, ν	0.27
Fracture Toughness, K_{Ic} [MPa x m ^{1/2}]	0.47
Knoop Hardness, $HK_{0.1/20}$	340
Heat Capacity (25 °C), C_p [J/g x K]	0.75
Thermal Diffusivity (25 °C), σ [10^{-7} m ² /sec]	2.92
Thermal Expansion, $\alpha_{20-300^\circ\text{C}}$ [10^{-7} /K]	145
Thermal Expansion, $\alpha_{20-40^\circ\text{C}}$ [10^{-7} /K]	125
Glass Transformation Temperature, T_g (°C)	375


IOG-2 Phosphate Laser Glass

For High Gain Applications


Erbium Absorption and Emission Cross Sections around 1540 nm

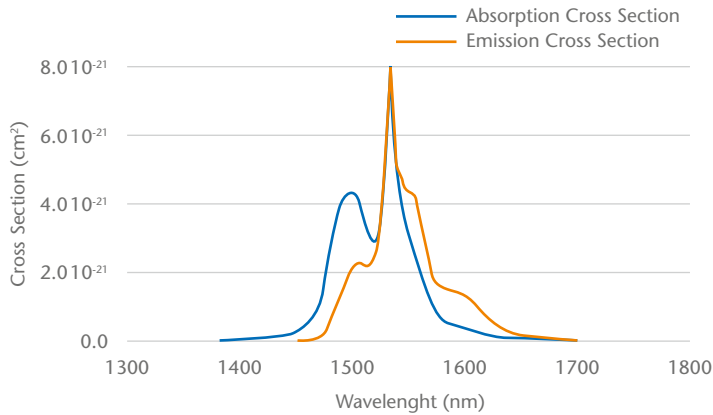

Ytterbium Absorption and Emission Cross Sections around 980 nm

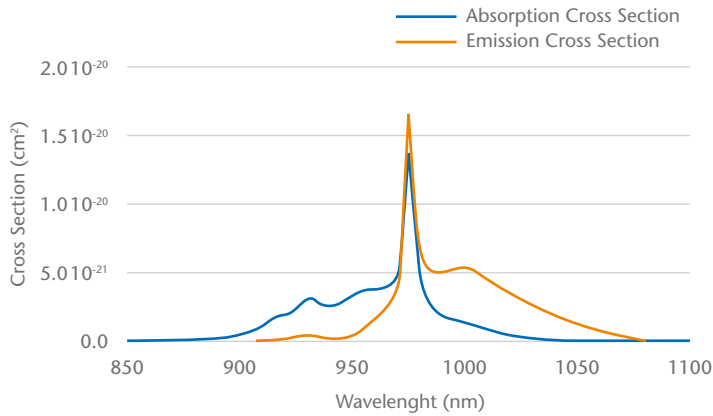

Erbium Absorption Cross Section around 980 nm

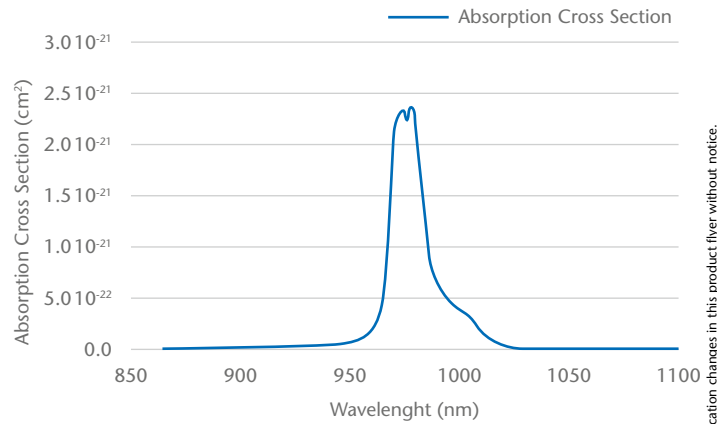

Version May 2013 | SCHOTT Advanced Optics reserves the right to make specification changes in this product flyer without notice.

Advanced Optics
SCHOTT North America, Inc.
400 York Avenue
Duryea, PA 18642
USA
Phone +1 570/457-7485
Fax +1 570/457-7330
info.optics@us.schott.com

www.us.schott.com/advanced_optics

SCHOTT
glass made of ideas