

IOG-1 Phosphate Laser Glass

For Ion Exchange Applications

IOG-1 is a chemically durable, sodium-aluminophosphate glass developed for use in active and passive waveguide devices, which are fabricated by ion exchange in a molten KNO_3 or AgNO_3 salt bath. Cumulative Er_2O_3 and Yb_2O_3 doping levels can be selected anywhere from 0 to 20wt%. IOG-1 devices are discussed in "Arrays of distributed-Bragg-reflector waveguide lasers at 1536 nm in Yb/Er codoped phosphate glass," Appl. Phys. Lett., Vol 74(6), 789-791 (1999).

Optical Properties

n_d	1.523
V_d	67.5
$n_{1000 \text{ nm}}$ (calculated)	1.515
$n_{1540 \text{ nm}}$ (calculated)	1.513

Erbium Laser Properties

Emission Maxima, λ (nm)	1534
Emission Cross Section at 1534 nm (10^{-21} cm^2)	6.6
Excited State Lifetime for the 1534 nm Band (ms)	10.7
Max Absorption Cross Section for 980 nm Pump Band (10^{-21} cm^2)	2.0

Ytterbium Laser Properties

Emission Maxima, λ (nm)	1002
Emission Cross Section at 1002 nm (10^{-21} cm^2)	5.4
Excited State Lifetime for the 1002 nm Band (ms)	1.4
Max Absorption Cross Section for 980 nm Pump Band (10^{-21} cm^2)	14.5

• Properties will vary slightly with doping content

Chemical Properties

Weight Loss in 50 °C Water [mg/($\text{cm}^2 \times \text{day}$)]	0.012
Acid Resistance SR pH = 0.3 at 25 °C	3.0
Alkali Resistance AR pH = 12 at 50 °C	4.3
Staining Resistance FR pH = 4.6 100 h at 25 °C	0
Climatic Resistance CR Water Vapor at 40–50 °C for 30 h	1


Physical Properties

Density, ρ [g/cm^3]	2.74
Thermal Conductivity (25 °C), κ [$\text{W}/\text{m} \times \text{K}$]	0.67
Young's Modulus, E [GPa]	61.2
Poisson's Ratio, ν	0.24
Fracture Toughness, K_{Ic} [$\text{MPa} \times \text{m}^{1/2}$]	0.54
Knoop Hardness, $\text{HK}_{0.1/20}$	380
Heat Capacity (25 °C), C_p [$\text{J}/\text{g} \times \text{K}$]	0.78
Thermal Diffusivity (25 °C), σ [$10^{-7} \text{ m}^2/\text{sec}$]	3.2
Thermal Expansion, $\alpha_{20-300^\circ\text{C}}$ [$10^{-7}/\text{K}$]	112
Thermal Expansion, $\alpha_{20-40^\circ\text{C}}$ [$10^{-7}/\text{K}$]	93
Glass Transformation Temperature, T_g (°C)	474


IOG-1 Phosphate Laser Glass

For Ion Exchange Applications


Erbium Absorption and Emission Cross Sections around 1540 nm

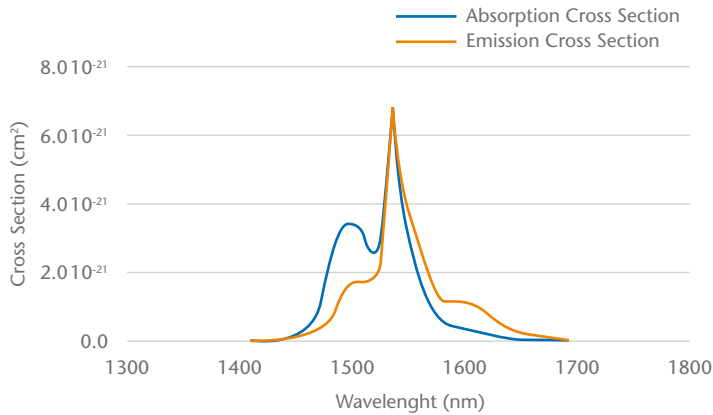

Ytterbium Absorption and Emission Cross Sections around 980 nm

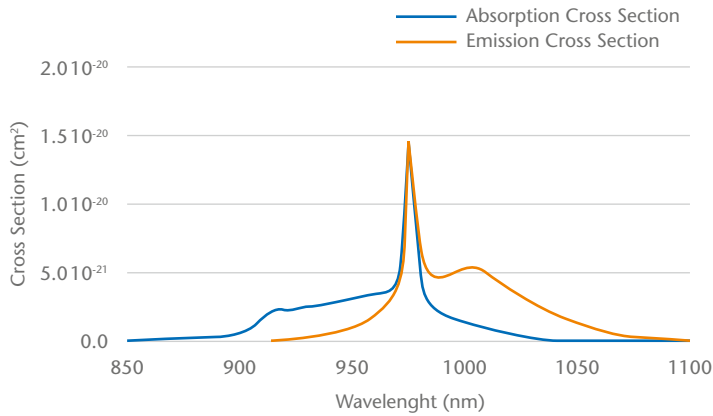

Erbium Absorption Cross Section around 980 nm

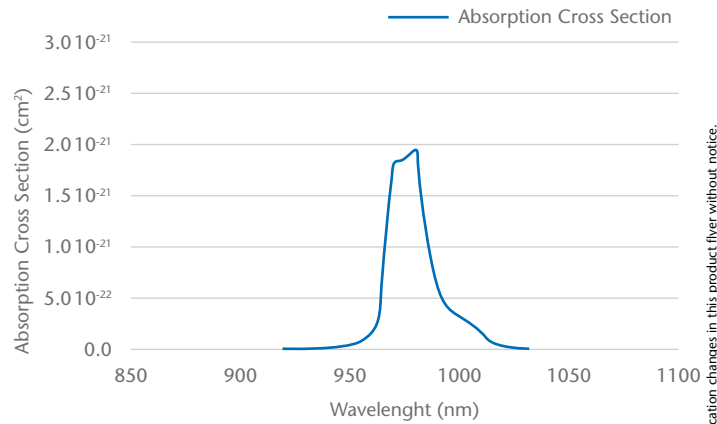

Version May 2013 | SCHOTT Advanced Optics reserves the right to make specification changes in this product flyer without notice.

Advanced Optics
SCHOTT AG
Hattenbergstrasse 10
55122 Mainz
Germany
Phone +49 (0)6131/66-1812
Fax +49 (0)3641/2888-9047
info.optics@schott.com

www.schott.com/advanced_optics

SCHOTT
glass made of ideas